



CALCULATION FORMULAS FREQUENTLY USED IN SHEET METAL

This time, we summarized a calculation formula that is frequently used in sheet metal, including the calculation of tonnage.

TONNAGE CALCULATION

In the punch press machine, the allowable tonnage depending on the machine. Use the calculation formula below to prevent from over tonnage.

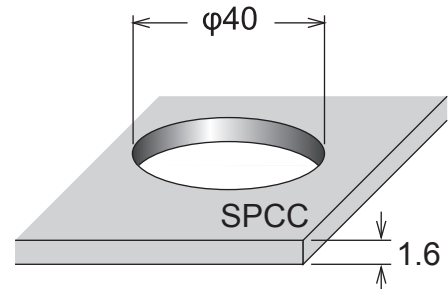
$$\text{Tonnage(ton)} = \frac{\text{Circumference(mm)} \times \text{Material thickness(mm)} \times \text{Shear resistance(kg/mm}^2\text{)}}{1000}$$

Circumference		Shear resistance by material	
Round	Shaped	Material	Shear resistance (kg/mm ²)
Diameter x 3.14	(Length dimension + Width dimension) x 2	Mild Steel	400
		SS400	450
Circumference = D x 3.14	Circumference = (A + B) x 2	Stainless Steel	600
		Aluminum	200
		Copper	300
		Brass	400

< Calculation example >

The tonnage when piercing φ40 to Mild Steel T=1.6mm

$$\frac{40 \times 3.14}{\text{Circumference}} \times \frac{1.6}{\text{Material thickness}} \times \frac{35}{\text{Shear resistance}} \div 1000 = 7 \text{ (ton)}$$



If you do not know the shear resistance, please use about 80% of the shear resistance = tensile strength as a standard.

ADVICE ON ONE POINT

If the tonnage exceeds the allowable tonnage of the machine, reduce the tonnage by the following method.


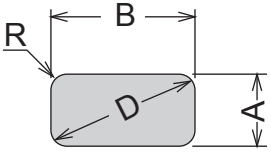
1. Put shear angle on punch edge. (Allows you to reduce tonnages around 10 to 50% by shear angle.)
2. Piercing several times. (Reducing tonnages by piercing several times)
3. When using cluster tooling, the tonnages can be reduced by making a difference in length of punch that makes same effect as shear angle.

CALCULATION FORMULAS FREQUENTLY USED IN SHEET METAL

MAKE A SELECTION OF TOOL STATION

Calculation of the diameter (diagonal dimension) of the cutting edge circumscribed circle is required to select the tool station.

Calculation of diameter (diagonal dimension) of cutting edge circumscribed circle

Rectangle shape	Rectangular shape with radius
	
$D = \sqrt{A^2 + B^2}$	$D = \sqrt{(A - 2 \times R)^2 + (B - 2 \times R)^2} + 2 \times R$



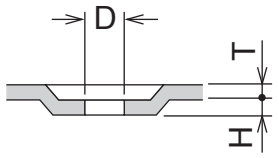
ADVICE ON ONE POINT

Normally, the size of the tool station is determined by calculating the dimension of the cutting edge circumscribing circle using the above formula and then comparing it with the turret layout. However, when processing thick materials, it is necessary to increase the station size by one size to prevent from miss stripping.

CALCULATING PRE-HOLE DIMENSION FOR FORMING

When forming processing, pre-holes may be processed as pre-processing. In that case, please calculate pre-holes referring to the following calculation formula.

Calculating pre-hole dimension for forming (Reference value for SPCC)

Chamfering	Burring	Burring for tapping			Emboss
		Size	Inner Dia.	Pre-hole	
		M2.6	φ2.1	φ1.2	
		M3	φ2.6	φ1.5	
		M4	φ3.4	φ2.0	
		M5	φ4.3	φ2.4	
		M6	φ5.1	φ2.8	
Pre-Hole = $\frac{(B \times 2) + A}{3}$	Pre-hole = $D + 1.8 \times T - 2 \times H$	Other dimension, Pre-hole = $0.53 \times D + 0.1$			Pre-hole = $D - (0.6 - 0.16 \times T) \times H$

ADVICE ON ONE POINT

Although forming shape is same, pre-hole dimension would be different depending on material. It is recommended that you try trial machining with reference to the above equation to obtain proper pre-hole dimension.

For More information,
please contact
CONIC tool sales desk.

CONIC Co., Ltd.

10-5 Taiheidai, Shoo-cho, Katsuta-gun,
Okayama 709-4321 Japan
Email: tools@conic.co.jp
https://www.conic.co.jp

CONIC PRECISION Co., Ltd.

55/22 Moo 4, Buengkumproy, Lumlukka,
Phatumthani 12150 Thailand
TEL: (662) 159-9870 FAX: (662) 159-9872
Email: conic_thai@conic.co.jp